



.....

**DATA SHEET:**  
**MSPB2 CW617N**

.....

**FREE MACHINING**



**High workability alloy and lead of less than 2%.**

The demand for alloys with reduced lead content, but with high machinability due to chip removal, has allowed the development of a high performance alloy. Inserted in the "Positive List" of the 4MS it is usable up to 10% of the surface of the domestic system of distribution of drinking water.

## NAME OF ALLOY

**UNI EN:** CW617N - CuZn40Pb2    **ASTM:** C37700    **DIN:** 2.0402    **BS:** CZ122    **GOST:** LS59-2

## CHEMICAL COMPOSITION UNI EN 12164 ED.2016

Cu	Pb	Sn	Fe	Ni*	Si*	Zn	Other elements
min. 57.0 max. 59.0 %	1.6 2.0 %	≤0.3 %	≤0.3 %	≤0.1 %	≤0.03 %	difference	≤0.2 %

\*Limitation according 4MS. Elements not listed must be ≤0.02 %.  
Group of restriction of the surface in contact with drinking water: B,D.

## HEAT TREATMENTS

### STRESS RELIEVING

Enables the redistribution of tensions induced by mechanical processing of cold plastic deformation, reducing the risk of stress corrosion cracking. The treatment consists of heating the items to 200°C - 250°C for 2 hours and cooling within the furnace. The validation of the stress relieving treatment can be performed with the ISO 6957 test.

### ANNEALING

Re-crystallizes the alloy, reducing its hardness and increasing its ductility. The temperature of the treatment varies from 450°C to 550°C for an amount of time relative to the required results. The high temperature can induce changes in the surface appearance and in the tolerance of the finished part.

## MECHANICAL PROPERTIES UNI EN 12164 ED.2016

Condition of material	Diameter in mm		Hardness HB*		Rm	Rp <sub>0.2</sub> N/mm <sup>2</sup>		Elongation %
	from	to (included)	min.	max.	min.	min.	max.	min.
M	All		As a product					
R360	6	80	-	-	360	-	320	20
H090	6	80	90	125	-	-	-	-
R430	2	40	-	-	430	220	-	10
H110	2	40	110	160	-	-	-	-
R500	2	14	-	-	500	350	-	5
H135	2	14	135	-	-	-	-	-

\*the hardness value is determined in the mid-range  
The standard condition produced by Almag is R500 from  $\varnothing > 6$  to  $\varnothing \leq 11$  and R430 from  $\varnothing > 11$  for Rm, or H110 for hardness. Any other conditions must be requested when ordering - subject to feasibility request.

TECHNOLOGICAL PROPERTIES		low	[Progress bar]					excellent
Structure	$\alpha+\beta$	Machinability	[Progress bar]					
Density	8.4 kg/cm <sup>3</sup>	Weldability	[Progress bar]					
Electrical conductivity	27% IACS	Hot forming	[Progress bar]					
Coeff. of thermal expansion	20.7 10 <sup>-6</sup> /K	Cold forming	[Progress bar]					
Thermal conductivity*	120 W/(m K)	Corrosion resistance**	Not resistant					
Specific heat	380 J/(kg K)							
Elasticity module	105 kN/mm <sup>2</sup>							
Melting point	880-895 °C							

\*at room temperature  
\*\*use care to ascertain compatibility with chemical substances

## DIMENSIONS, TOLERANCES, AND STRAIGHTNESS UNI EN 12164 ED.2016


ROUND section bar					HEXAGONAL and SQUARE		
Nominal diameter (mm)		TOLERANCES			Nominal key (mm)		Tolerance mm
from	to included	Class A	Class B	Class C	from	to included	
6	10	0 - 0.06	0 - 0.036	0 - 0.025	6	10	0 - 0.09
10	18	0 - 0.07	0 - 0.043		10	18	0 - 0.11
18	30	0 - 0.08	0 - 0.052		18	30	0 - 0.13
30	50	0 - 0.16			30	50	0 - 0.16
50	80	0 - 0.19			50	60	0 - 0.19

The standard tolerance for the round bar is Class A. Any different tolerances must be agreed upon when ordering  
Semi-finished products can be supplied from Ø63 to Ø80 mm with Class A tolerances

Diameter (mm)	Length of bar (mm)	Tolerance (mm)	Diameter or Key (mm)	Deviation from straightness in mm	
				Every 400 mm	Every m of length L ≥ 1
2	30	3000 o 4000	+/- 50		
30	50	3000 o 4000	+/- 100		
50	80	3000	+/- 100		
<b>Round section bar</b>					
10	50		0.4	1.0 x L	
<b>Hexagonal and square section bar</b>					
10	50		0.6	1.5 x L	

## BAR FINISHING AND PACKAGING

Diameter or Key (mm)		Chamfer Length L mm		Tip Length L mm	
5	10	0.2	1.5	2	7
10	20	0.2	2	3	10
20	30	0.2	3	4	12

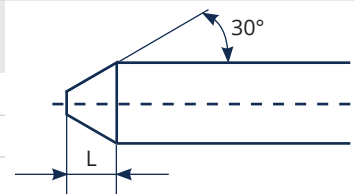

Unless otherwise specified by the buyer, the shape of the ends of products larger than 30 mm is up to the supplier

Ends of round bars	finishing with chamfer and tip up to and including Ø40 mm finishing with chamfer and cut greater than Ø40 mm
Ends of hexagonal bars	finishing with chamfer and cut
Bar surface	pickled
Packaging	1000 kg bundle – 3/5 metal straps different bundle packagings and quantities are possible upon request
Identification	adhesive label on bundle strap
Stress relieving	the polygonal bar was subjected to stress relieving treatment

COMPANY WITH  
MANAGEMENT SYSTEM  
CERTIFIED BY DNV GL  
= ISO 9001 =  
= ISO 14001 =  
= OHSAS 18001 =



[www.almag.it](http://www.almag.it)

**ALMAG S.p.A.** AZIENDA LAVORAZIONI METALLURGICHE E AFFINI GNUTTI  
*Single-member S.p.A.* *A subsidiary of HUG S.p.A.*

25030 Roncadelle (BS) - Via Vittorio Emanuele II n. 39 - Fully paid share capital € 2.000.000  
Tel. +39 030 2789511 - Fax +39 030 2789680 (admin.) - Fax +39 030 2789690 (sales)  
F.C./VAT and Brescia Chamber of Comm. Reg. No. 03368970988 - R.E.A. No. 528368 - Cert. email [almagspa@legalmail.it](mailto:almagspa@legalmail.it)

